

Celxpert Energy Corporation


Battery Pack *UN38.3 Test Report*

Customer:	SRAM Corporation
Model:	M/N 25402
Nominal voltage:	7.4V
Rated Capacity:	Typ.300mAh Min.290mAh/2.2Wh
Issue Date:	2020-10-07



1.UN38.3 Lithium Battery Test Summary

Edition of UN Manual of Tests and Criteria Used		UN38.3S-T/SG/AC.10/11/Rev.6/Amend.1	
Customer	SRAM Corporation	Sample type	Rechargeable Lithium Ion Battery
Model Name	M/N 25402	Pack Configuration	2S1P
Rating	7.4Vdc,Typ.300mAh/ Min.290mAh 2.2Wh	Battery weight	23 ± 2g
Cell Factory/Model	SYnergy ScienTech Corp. AHB601930T	Physical Description	Prismatic
Factory Address	No.128, Gong Wu Rd, Wu Lin Vil, Lung Tan, Taoyuan, Taiwan, 325, R.O.C	Laboratory Address	NO.1111, Hanpu Road, Yushan Town, Kunshan City, Jiangsu Province, P.R. China
Factory Name	Celxpert Energy Corporation	Laboratory Name	CPK LAB
Factory Tel	03-4899054	Laboratory Tel	+86-512-57775999
Factory E-mail	Ellie_Peng@celxpert.com.tw	Lab E-mail	Frank_Gao@cn.celxpert.com
Factory Web	www.celxpert.com.tw	Laboratory Web	www. celxpert.com.tw
Client Date	2020/08/10	Completing Data	2020/09/29
Item	Test Item	Test Result(Pass/Fail)	
38.3.4.1 T1	Altitude simulation	Pass	
38.3.4.1 T2	Thermal	Pass	
38.3.4.1 T3	Vibration	Pass	
38.3.4.1 T4	Shock	Pass	
38.3.4.1 T5	External Short Circuit	Pass	
38.3.4.1 T6	Crush	Pass	
38.3.4.1 T7	Overcharge	Pass	
38.3.4.1 T8	Forced Discharge	Pass	

Approved By	Checked By	Prepared By
		
Section manager	Section manager	Engineer

2. Test items and quantity

T1. Altitude simulation

T5. External short circuit

T2. Thermal

T6. Crush/ Impact

T3. Vibration


T7. Overcharge

T4. Shock

T8. Forced Discharge

summary table of required test for rechargeable cells and batteries										
		T1	T2	T3	T4	T5	T6	T7	T8	SUM
Cell	First cycle, 50% charged state						5			30
	25th cycle, 50% charged state						5			
	First cycle, fully discharged state								10	
	25th cycle, fully discharged state								10	
<12kg Small batteries	First cycle, fully charged state	4						4		16
	25th cycle, fully charged state	4						4		
>12kg Large batteries	First cycle, fully charged state	2						2		8
	25th cycle, fully charged state	2						2		

3. Test Procedure

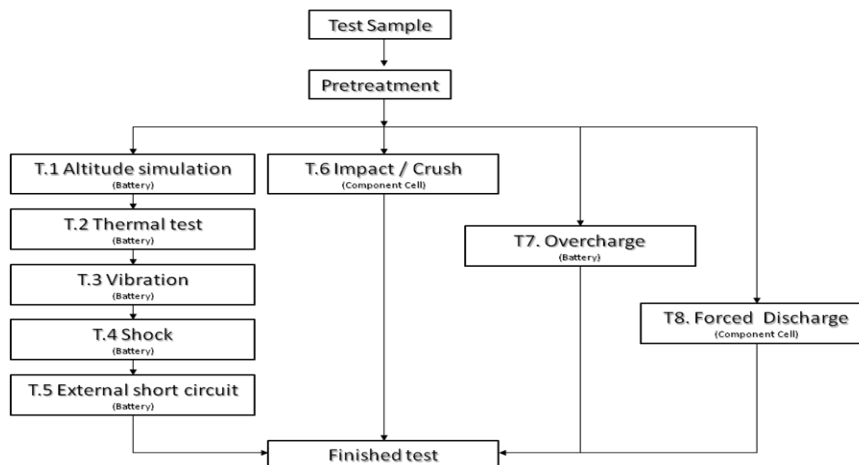

4.Photo of The Sample

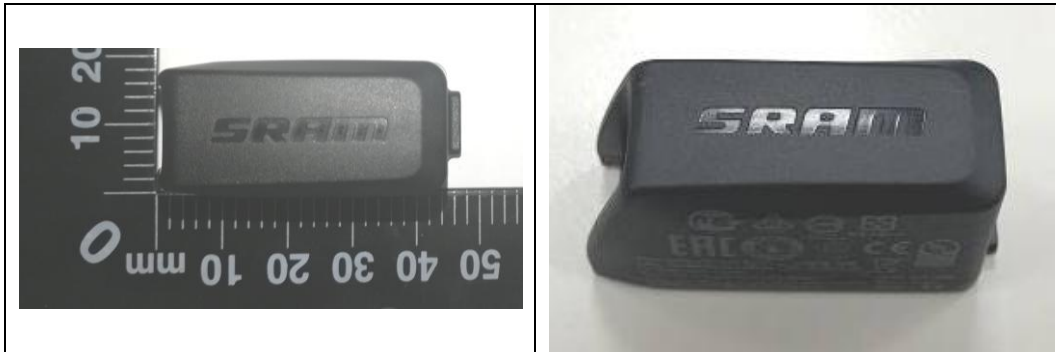


Photo 1 Front



Photo 2 Rear

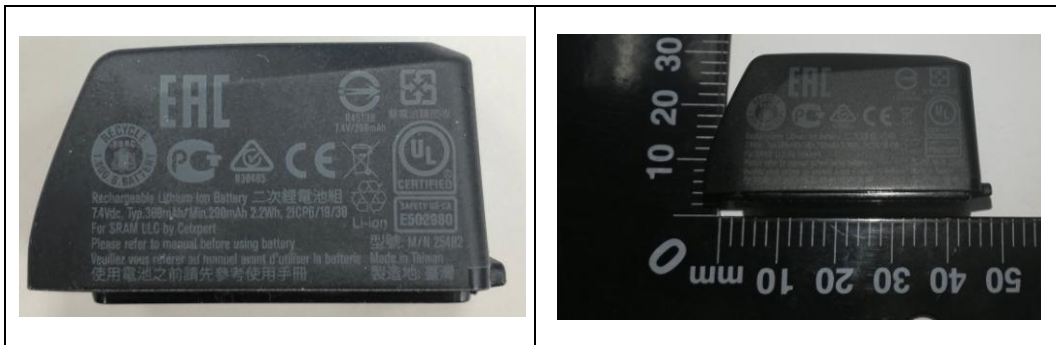


Photo 3 Label



Photo 4 Label

5. Test method and verdict

Clause	Requirements	Verdict							
Table 38.3.1	Mass loss means a loss of mass that exceeds the values in table 38.3.1 below								
	<p style="text-align: center;">Table 38.3.1: Mass loss limit</p> <table border="1" style="margin-left: auto; margin-right: auto;"> <thead> <tr> <th>Mass M of cell or battery</th> <th>Mass loss limit</th> </tr> </thead> <tbody> <tr> <td>M<1g</td> <td>0.5%</td> </tr> <tr> <td>1g ≤ M ≤ 75g</td> <td>0.2%</td> </tr> <tr> <td>M>75g</td> <td>0.1%</td> </tr> </tbody> </table>	Mass M of cell or battery	Mass loss limit	M<1g	0.5%	1g ≤ M ≤ 75g	0.2%	M>75g	0.1%
Mass M of cell or battery	Mass loss limit								
M<1g	0.5%								
1g ≤ M ≤ 75g	0.2%								
M>75g	0.1%								
38.3.4.1	T1 :Altitude simulation								
	This test simulates air transport under low-pressure conditions	No leakage no venting no disassemble no rupture no fire. voltage not less than 90% Mass loss limit (see table 38.3.1)							
	Test cells and batteries shall be stored at a pressure of 11.6kPa or less for at least six hour at ambient temperature (20±5°C)								
Cells and batteries meet this requirement if there is no leakage, no venting, no disassemble, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states									
38.3.4.2	T2:Thermal test								
	This test assesses cell and battery seal integrity and internal electrical connections. The test is conducted using rapid and extreme temperature changes.	No leakage no venting no disassemble no rupture no fire voltage not less than 90% Mass loss limit (see table 38.3.1).							
	Test cells and batteries are to be stored for at least six hours at a test temperature equal to 72±2°C, followed by storage for at least six hours at a test temperature equal to -40±2°C. The maximum time interval between test temperature extremes is 30 minutes. This procedure is to be repeated until 10 total cycles are complete, after which all test cells and batteries are to be stored for 24 hours at ambient temperature (20 ± 5°C). For large cells and batteries the duration of exposure to the test temperature extremes should be at least 12 hours.								
Cells and batteries meet this requirement if there is no leakage, no venting, no disassemble, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.									
38.3.4.3	T3:Vibration								
	This test simulates vibration during transport	No leakage no venting no disassemble no rupture no fire. voltage not less than 90% Mass loss limit (see table 38.3.1)							
	Cells and batteries are firmly secured to the platform of the vibration machine without distorting the cells in such a manner as to faithfully transmit the vibration. The vibration shall be a sinusoidal waveform with a logarithmic sweep between 7 Hz and 200 Hz and back to 7 Hz traversed in 15 minutes. This cycle shall be repeated 12 times for a total of 3 hours for each of three mutually perpendicular mounting positions of the cell. One of the directions of vibration must be perpendicular to the terminal face.								
	For cells and small batteries: from 7 Hz a peak acceleration of 1gn is maintained until 18 Hz is reached. The amplitude is then maintained at 0.8 mm (1.6 mm total excursion) and the frequency increased until a peak acceleration of 8gn occurs (approximately 50 Hz). A peak acceleration of 8gn is then maintained until the frequency is increased to 200 Hz.								
	For large batteries: from 7 Hz to a peak acceleration of 1gn is maintained until 18 Hz is reached. The amplitude is then maintained at 0.8 mm (1.6 mm total excursion) and the frequency increased until a peak acceleration of 2gn occurs (approximately 25 Hz). A peak acceleration of 2gn is then maintained until the frequency is increased to 200 Hz.								
Cells and batteries meet this requirement if there is no leakage, no venting, no disassemble, no rupture and no fire during the test and after the test and if the open circuit voltage of each test cell or battery directly after testing in its third perpendicular mounting position is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.									

Clause	Requirements	Verdict
38.3.4.4	T4:Shock	No leakage no venting no disassemble no rupture no fire. voltage not less than 90% Mass loss limit (see table 38.3.1)
	This test assesses the robustness of cells and batteries against cumulative shocks	
	Test cells and batteries shall be secured to the testing machine by means of a rigid mount which will support all mounting surfaces of each test battery	
	Each cell shall be subjected to a half-sine shock of peak acceleration of 150gn and pulse duration of 6 milliseconds. Alternatively, large cells may be subjected to a half-sine shock of peak acceleration of 50gn and pulse duration of 11 milliseconds.	
	Each battery shall be subjected to a half-sine shock of peak acceleration depending on the mass of the battery. The pulse duration shall be 6 milliseconds for small batteries and 11 milliseconds for large batteries. The formulas below are provided to calculate the appropriate minimum peak accelerations. Each cell or battery is subjected to three shocks in the positive direction followed by three shocks in the negative direction of each of three mutually perpendicular mounting positions of the cell for a total of 18 shocks.	
Cells and batteries meet this requirement if there is no leakage, no venting, no disassemble, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.		
38.3.4.5	T5:External short circuit	no disassemble no rupture no fire. Packs exterior peak temperature <170°C Mass loss limit (see table 38.3.1)
	This test simulates an external short circuit	
	The cell or battery to be tested shall be shall be heated for a period of time necessary to reach a homogeneous stabilized temperature of 57±4°C, measured on the external case. This period of time depends on the size and design of the cell or battery and should be assessed and documented. If this assessment is not feasible, the exposure time shall be at least 6 hours for small cells and small batteries, and 12 hours for large cells and large batteries. Then the cell or battery at 57±4°C shall be subjected to one short circuit condition with a total external resistance of less than 0.1 ohm.	
	This short circuit condition is continued for at least one hour after the cell or battery external case temperature has returned to 57 ± 4 °C, or in the case of the large batteries, has decreased by half of the maximum temperature increase observed during the test and remains below that value. The short circuit and cooling down phases shall be conducted at least at ambient temperature.	
	Cells and batteries meet this requirement if their external temperature does not exceed 170°C and there is no disassemble, no rupture and no fire within six hours of this test.	

Clause	Requirements	Verdict
38.3.4.6	T6: Crush /Impact	no disassemble no rupture no fire. not exceed 170°C Mass loss limit (see table 38.3.1)
	These tests simulate mechanical abuse from an impact or crush that may result in an internal short circuit.	
	Impact applicable to cylindrical cells not less than 18.00 in diameter.	
	The test sample cell or component cell is to be placed on a flat smooth surface. A 15.8mm±0.1mm diameter, at least 6cm long, or the longest dimension of the cell, whichever is greater, Type 316 stainless steel bar is to be placed across the centre of the sample. A 9.1 kg ± 0.1kg mass is to be dropped from a height of 61 ± 2.5 cm at the intersection of the bar and sample in a controlled manner using a near frictionless, vertical sliding track or channel with minimal drag on the falling mass. The vertical track or channel used to guide the falling mass shall be oriented 90 degrees from the horizontal supporting surface. The test samples is to be impacted with its longitudinal axis parallel to the flat surface and perpendicular to the longitudinal axis of the 15.8mm±0.1mm diameter curved surface lying across the centre of the test samples. Each sample is to be subjected to only a single impact.	
	Crush applicable to prismatic, pouch, coin/button cells and cylindrical cells less than 18mm in diameter.	
	A cell or component cell is to be crushed between two flat surfaces. The crushing is to be gradual with a speed of approximately 1.5cm/s at the first point of contact. The crushing is to be continued until the first of the three options below is reached. (a) The applied force reaches 13kN±0.78kN; Example : The force shall be applied by a hydraulic ram with a 32 mm diameter piston until a pressure of 17 MPa is reached on the hydraulic ram (b) The voltage of the cell drops by at least 100mV; or (c) The cell is deformed by 50% or more of its original thickness. Once the maximum pressure has been obtained, the voltage drops by 100mV or more, or the cell is deformed by at least 50% of its original thickness, the pressure shall be released A prismatic or pouch cell shall be crushed by applying the force to the widest side. A button/coin cell shall be crushed by applying the force on its flat surfaces. For cylindrical cells, the crush force shall be applied perpendicular to the longitudinal axis. Each test cell or component cell is to be subjected to one crush only. The test Samples shall be observed for a further 6 h. The test shall be conducted using test cells or component cells that have not previously been subjected to other tests.	
	Cells and component cells meet this requirement if their external temperature does not exceed 170°C and there is no disassemble and no fire during the test and within six hours after this test.	

Clause	Requirements	Verdict
38.3.4.7	T7:Overcharge	
	This test evaluates the ability of a rechargeable battery or a single cell rechargeable battery to withstand an overcharge condition	No disassemble no fire. Mass loss limit (see table 38.3.1)
	<p>The charge current shall be twice the manufacturer’s recommended maximum continuous charge current. The minimum voltage of the test shall be as follows:</p> <p>(a) When the manufacturer’s recommended charge voltage is not more than 18V, the minimum voltage of the test shall be the lesser of two times the maximum charge voltage of the battery or 22V.</p> <p>(b) When the manufacturer’s recommended charge voltage is more than 18V, the minimum voltage of the test shall be 1.2 times the maximum charge voltage.</p> <p>Tests are to be conducted at ambient temperature; the duration of the test shall be 24 hours</p>	
	Rechargeable batteries meet this requirement if there is no disassemble and no fire during the test and within seven days after the test.	
	T8:Forced discharge	
38.3.4.8	This test evaluates the ability of a primary or a rechargeable cell to withstand a forced discharge condition	
	<p>Each cell shall be forced discharged at ambient temperature by connecting it in series with a 12V D.C. power supply at an initial current equal to the maximum discharge current specified by the manufacturer.</p> <p>The specified discharge current is to be obtained by connecting a resistive load of the appropriate size and rating in series with the test cell. Each cell shall be forced discharged for a time interval (in hours) equal to its rated capacity divided by the initial test current (in ampere).</p>	
	Primary or rechargeable cells meet this requirement if there is no disassembly and no fire during the test and within seven days after the test.	

6.Test Data

38.3.4.1		T1.Altitude simulation						
Test Equipment	Digital Meter :Q-153 , Vacuum Oven :Q-0443 , Scales :E-1126							
Test Period	Start:2020/09/09		End:2020/09/09					
Altitude Simulation Test on Charged Packs								
No.	Before		After		voltage residue	mass loss	other event	
	OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)		
First cycle								
1	8.366	22.169	8.348	22.168	99.78%	0.00%	O	
2	8.347	22.235	8.336	22.234	99.87%	0.00%	O	
3	8.343	22.324	8.323	22.322	99.76%	0.01%	O	
4	8.352	22.228	8.339	22.227	99.84%	0.00%	O	
25 cycles								
5	8.364	22.247	8.338	22.244	99.69%	0.01%	O	
6	8.377	22.231	8.347	22.229	99.64%	0.01%	O	
7	8.331	22.235	8.303	22.233	99.66%	0.01%	O	
8	8.370	22.295	8.345	22.294	99.70%	0.00%	O	
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire								
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire								
38.3.4.2		T2.Thermal test						
Test Equipment	Digital Meter: Q-153 , Programmable Thermal Tester:Q-0483 , Scales:E-1126							
Test Period	Start:2020/09/10		End:2020/09/16					
Thermal Test on Charged Packs								
No.	Before		After		voltage residue	mass loss	other event	
	OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)		
First cycle								
1	8.348	22.168	8.322	22.165	99.69%	0.01%	O	
2	8.336	22.234	8.319	22.237	99.80%	-0.01%	O	
3	8.323	22.322	8.274	22.322	99.41%	0.00%	O	
4	8.339	22.227	8.312	22.230	99.68%	-0.01%	O	
25 cycles								
5	8.338	22.244	8.324	22.244	99.83%	0.00%	O	
6	8.347	22.229	8.326	22.227	99.75%	0.01%	O	
7	8.303	22.233	8.288	22.231	99.82%	0.01%	O	
8	8.345	22.294	8.296	22.295	99.41%	0.00%	O	
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire								
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire								

38.3.4.3		T3.Vibration					
Test Equipment	Digital Meter : Q-153 , Vibration Tester :Q-300 , Scales :E-1126						
Test Period	Start:2020/09/17		End:2020/09/21				
Vibration Test on Charged Packs							
No.	Before		After		voltage residue	mass loss	other event
	OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
First cycle							
1	8.322	22.165	8.318	22.165	99.95%	0.00%	O
2	8.319	22.237	8.317	22.237	99.98%	0.00%	O
3	8.274	22.322	8.266	22.321	99.90%	0.00%	O
4	8.312	22.230	8.304	22.231	99.90%	0.00%	O
25 cycles							
5	8.324	22.244	8.323	22.243	99.99%	0.00%	O
6	8.326	22.227	8.316	22.227	99.88%	0.00%	O
7	8.288	22.231	8.283	22.232	99.94%	0.00%	O
8	8.296	22.295	8.292	22.294	99.95%	0.00%	O
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire							
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire							
38.3.4.4		T4. Shock					
Test Equipment	Digital Meter: Q-153 , Shock Tester:Q-154 , Scales:E-1126						
Test Period	Start:2020/09/22		End:2020/09/25				
Shock Test on Charged Packs							
No.	Before		After		voltage residue	mass loss	other event
	OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
First cycle							
1	8.318	22.165	8.317	22.166	99.99%	0.00%	O
2	8.317	22.237	8.310	22.238	99.92%	0.00%	O
3	8.266	22.321	8.262	22.320	99.95%	0.00%	O
4	8.304	22.231	8.294	22.232	99.88%	0.00%	O
25 cycles							
5	8.323	22.243	8.317	22.243	99.93%	0.00%	O
6	8.316	22.227	8.312	22.227	99.95%	0.00%	O
7	8.283	22.232	8.277	22.231	99.93%	0.00%	O
8	8.292	22.294	8.288	22.294	99.95%	0.00%	O
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire							
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire							

38.3.4.5	T5. Short circuit																																													
Test Equipment	Digital Meter: Q-153 , DC electronic load:Q-075 , Oven:Q-171																																													
Test Period	Start:2020/09/28 End:2020/09/29																																													
<table border="1"> <thead> <tr> <th colspan="3">Short Circuit Test on Charged Packs</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr> <td colspan="3" style="text-align: center;">First cycle</td> </tr> <tr> <td>1</td> <td>57.59</td> <td>O</td> </tr> <tr> <td>2</td> <td>57.75</td> <td>O</td> </tr> <tr> <td>3</td> <td>57.96</td> <td>O</td> </tr> <tr> <td>4</td> <td>56.96</td> <td>O</td> </tr> <tr> <td colspan="3" style="text-align: center;">25 cycles</td> </tr> <tr> <td>5</td> <td>57.70</td> <td>O</td> </tr> <tr> <td>6</td> <td>56.04</td> <td>O</td> </tr> <tr> <td>7</td> <td>57.45</td> <td>O</td> </tr> <tr> <td>8</td> <td>57.88</td> <td>O</td> </tr> <tr> <td colspan="3">Note: D-Disassembly ; R-Rupture ; F-Fire</td> </tr> <tr> <td colspan="3">O- No Disassembly , No Rupture , No Fire</td> </tr> </tbody> </table>		Short Circuit Test on Charged Packs			No.	Max. Temp.(°C)	Other event	First cycle			1	57.59	O	2	57.75	O	3	57.96	O	4	56.96	O	25 cycles			5	57.70	O	6	56.04	O	7	57.45	O	8	57.88	O	Note: D-Disassembly ; R-Rupture ; F-Fire			O- No Disassembly , No Rupture , No Fire					
Short Circuit Test on Charged Packs																																														
No.	Max. Temp.(°C)	Other event																																												
First cycle																																														
1	57.59	O																																												
2	57.75	O																																												
3	57.96	O																																												
4	56.96	O																																												
25 cycles																																														
5	57.70	O																																												
6	56.04	O																																												
7	57.45	O																																												
8	57.88	O																																												
Note: D-Disassembly ; R-Rupture ; F-Fire																																														
O- No Disassembly , No Rupture , No Fire																																														
38.3.4.6	T6. Crush /Impact																																													
Test Equipment	Digital Meter: Q-153 Data Logger:Q-152 Impact tester :Q-231/ Crush tester:Q-0437																																													
Test Period	Start:2020/09/10 End:2020/09/11																																													
<table border="1"> <thead> <tr> <th colspan="3">Crush Test</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr> <td colspan="3" style="text-align: center;">First cycle</td> </tr> <tr> <td>1</td> <td>22.12</td> <td>O</td> </tr> <tr> <td>2</td> <td>23.56</td> <td>O</td> </tr> <tr> <td>3</td> <td>24.11</td> <td>O</td> </tr> <tr> <td>4</td> <td>22.97</td> <td>O</td> </tr> <tr> <td>5</td> <td>22.53</td> <td>O</td> </tr> <tr> <td colspan="3" style="text-align: center;">25 cycles</td> </tr> <tr> <td>6</td> <td>23.47</td> <td>O</td> </tr> <tr> <td>7</td> <td>22.32</td> <td>O</td> </tr> <tr> <td>8</td> <td>22.75</td> <td>O</td> </tr> <tr> <td>9</td> <td>24.08</td> <td>O</td> </tr> <tr> <td>10</td> <td>22.61</td> <td>O</td> </tr> <tr> <td colspan="3">Note: D-Disassembly ; F-Fire / O-No Disassembly , No Fire</td> </tr> </tbody> </table>		Crush Test			No.	Max. Temp.(°C)	Other event	First cycle			1	22.12	O	2	23.56	O	3	24.11	O	4	22.97	O	5	22.53	O	25 cycles			6	23.47	O	7	22.32	O	8	22.75	O	9	24.08	O	10	22.61	O	Note: D-Disassembly ; F-Fire / O-No Disassembly , No Fire		
Crush Test																																														
No.	Max. Temp.(°C)	Other event																																												
First cycle																																														
1	22.12	O																																												
2	23.56	O																																												
3	24.11	O																																												
4	22.97	O																																												
5	22.53	O																																												
25 cycles																																														
6	23.47	O																																												
7	22.32	O																																												
8	22.75	O																																												
9	24.08	O																																												
10	22.61	O																																												
Note: D-Disassembly ; F-Fire / O-No Disassembly , No Fire																																														

38.3.4.7	T7. Overcharge																																																																												
Test Equipment	Digital Meter:Q-153 , Data Logger:Q-152 ,Power Supply unit:Q-236/Q-148/Q-150																																																																												
Test Period	Start:2020/08/10		End:2020/08/17																																																																										
<table border="1"> <thead> <tr> <th colspan="5">Overcharge Test on Charged Packs</th> </tr> <tr> <th>No.</th> <th>Charge Voltage(V)</th> <th>Charge Current(A)</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr> <td colspan="5" style="text-align:center">First cycle</td> </tr> <tr> <td>9</td> <td rowspan="4">16.8</td> <td rowspan="4">0.58</td> <td>23.00</td> <td>O</td> </tr> <tr> <td>10</td> <td>24.27</td> <td>O</td> </tr> <tr> <td>11</td> <td>22.49</td> <td>O</td> </tr> <tr> <td>12</td> <td>23.07</td> <td>O</td> </tr> <tr> <td colspan="5" style="text-align:center">25 cycles</td> </tr> <tr> <td>13</td> <td rowspan="4">16.8</td> <td rowspan="4">0.58</td> <td>23.46</td> <td>O</td> </tr> <tr> <td>14</td> <td>22.57</td> <td>O</td> </tr> <tr> <td>15</td> <td>22.25</td> <td>O</td> </tr> <tr> <td>16</td> <td>23.93</td> <td>O</td> </tr> </tbody> </table> <p>Note: D-Disassembly ; F-Fire / O-No Disassembly ,No Fire</p>						Overcharge Test on Charged Packs					No.	Charge Voltage(V)	Charge Current(A)	Max. Temp.(°C)	Other event	First cycle					9	16.8	0.58	23.00	O	10	24.27	O	11	22.49	O	12	23.07	O	25 cycles					13	16.8	0.58	23.46	O	14	22.57	O	15	22.25	O	16	23.93	O																								
Overcharge Test on Charged Packs																																																																													
No.	Charge Voltage(V)	Charge Current(A)	Max. Temp.(°C)	Other event																																																																									
First cycle																																																																													
9	16.8	0.58	23.00	O																																																																									
10			24.27	O																																																																									
11			22.49	O																																																																									
12			23.07	O																																																																									
25 cycles																																																																													
13	16.8	0.58	23.46	O																																																																									
14			22.57	O																																																																									
15			22.25	O																																																																									
16			23.93	O																																																																									
38.3.4.8	T8. Forced discharge																																																																												
Test Equipment	Digital Meter:Q-153 Data logger:Q-160 Power Supply unit:Q-0474/Q-0475/-0476																																																																												
Test Period	Start:2020/09/10		End:2020/09/24																																																																										
<table border="1"> <thead> <tr> <th colspan="3">Forced discharge are first cycle in fully discharged</th> <th colspan="3">Forced discharge are after 25 cycles ending in fully discharged</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr> <td>11</td> <td>21.32</td> <td>O</td> <td>21</td> <td>22.52</td> <td>O</td> </tr> <tr> <td>12</td> <td>21.09</td> <td>O</td> <td>22</td> <td>22.63</td> <td>O</td> </tr> <tr> <td>13</td> <td>22.86</td> <td>O</td> <td>23</td> <td>21.75</td> <td>O</td> </tr> <tr> <td>14</td> <td>23.01</td> <td>O</td> <td>24</td> <td>21.86</td> <td>O</td> </tr> <tr> <td>15</td> <td>22.75</td> <td>O</td> <td>25</td> <td>23.01</td> <td>O</td> </tr> <tr> <td>16</td> <td>22.96</td> <td>O</td> <td>26</td> <td>22.96</td> <td>O</td> </tr> <tr> <td>17</td> <td>21.48</td> <td>O</td> <td>27</td> <td>21.52</td> <td>O</td> </tr> <tr> <td>18</td> <td>21.33</td> <td>O</td> <td>28</td> <td>21.65</td> <td>O</td> </tr> <tr> <td>19</td> <td>21.86</td> <td>O</td> <td>29</td> <td>22.76</td> <td>O</td> </tr> <tr> <td>20</td> <td>22.77</td> <td>O</td> <td>30</td> <td>22.83</td> <td>O</td> </tr> </tbody> </table> <p>Note:D-Disassembly ; F-Fire / O-No Disassembly , No Fire</p>						Forced discharge are first cycle in fully discharged			Forced discharge are after 25 cycles ending in fully discharged			No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event	11	21.32	O	21	22.52	O	12	21.09	O	22	22.63	O	13	22.86	O	23	21.75	O	14	23.01	O	24	21.86	O	15	22.75	O	25	23.01	O	16	22.96	O	26	22.96	O	17	21.48	O	27	21.52	O	18	21.33	O	28	21.65	O	19	21.86	O	29	22.76	O	20	22.77	O	30	22.83	O
Forced discharge are first cycle in fully discharged			Forced discharge are after 25 cycles ending in fully discharged																																																																										
No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event																																																																								
11	21.32	O	21	22.52	O																																																																								
12	21.09	O	22	22.63	O																																																																								
13	22.86	O	23	21.75	O																																																																								
14	23.01	O	24	21.86	O																																																																								
15	22.75	O	25	23.01	O																																																																								
16	22.96	O	26	22.96	O																																																																								
17	21.48	O	27	21.52	O																																																																								
18	21.33	O	28	21.65	O																																																																								
19	21.86	O	29	22.76	O																																																																								
20	22.77	O	30	22.83	O																																																																								